

Research Article

Open Access

Frequencies of Failure In The Case of Ceramic Veneer Treatment and the Presence Of Composite Fillings: About A Clinical Trial

Soraya Dendouga

Lecturer Class A in Dental Prosthesis, CHU LAMINE DEBAGHINE, Alger, Algeria

ABSTRACT

Introduction: The restoration of teeth with composite ceramic veneers has always been a subject of controversy: for some authors the presence of such restorations is a source of failure while for others not necessarily.

Material and Method: Our study; is a randomized clinical trial comparing three types of crown preparations for bonded ceramic veneers. Our clinical trial which evaluated 264 bonded veneers in 73 patients included 235 living teeth and 29 mortified teeth that underwent endodontic treatment. Among the secondary objectives of this study: the evaluation of the durability of ceramic veneers bonded to teeth with composite restorations.

Results: The Chi-square test of the occurrence of events according to the unblocked / blocked character gives a $p = 0.05$ ($p \leq 0.05$) so the difference is significant.

Conclusion: The presence of composite fillings affected the survival rate of veneers in our study.

*Corresponding author

Soraya Dendouga, Lecturer Class A in Dental Prosthesis, Chu Lamine Debaghine, Alger, Algeria. E-mail: s.dendouga@gmail.com

Received: December 21, 2021; **Accepted:** December 29, 2021; **Published:** January 05, 2022

Introduction

In a society concerned with aesthetics, patient demand more frequently directs us to restorations invisible to their eyes. Adhesive dentistry has been able to respond not only to these growing aesthetic requirements but also to the continuing desire of practitioners to be as minimally mutilating as possible in their practice.

Among the aspects of this dentistry, ceramic veneers occupy an important place. This technique, which has become widely accepted in recent years, has given rise to the reflection of several researchers: preparation techniques, ceramic materials and glues; have been evaluated in different clinical and laboratory studies. We conducted a randomized clinical trial which focused on the comparison of the different types of coronary preparations (main objective). Among the secondary objectives of this trial was to know if the presence of composite fillings on the abutment teeth was a determining factor for the durability of ceramic veneers.

Material and Methods

Study Population

The subjects are recruited from among those who come to the dental prosthesis service at the Mustapha university hospital in Algiers.

The diagnosis of anomaly; color ; form ; minor structure or malposition will be objectified to the naked eye during clinical examination.

Subjects comparable by one of the anomalies cited and diagnosed will be treated by one of the techniques determined by random draw.

Selection Criteria

Inclusion Criteria

Any anterior tooth with:

A typical color abnormality: amelogenesis imperfecta due to tetracyclines; fluorosis; colorings due to age, coloring of external origin (tea, coffee or tobacco) by infiltration of the tissues; teeth discolored without loss of substance;

An anomaly of form: microdontia; atypical form case of conoid incisors;

An anomaly of structure or texture: dysplasia, dystrophy, erosion, attrition, mechanical or chemical abrasion and coronary fracture; A minor rotational malposition.

Our study will concern both men and women, but whatever the case, we will only include patients deemed reliable, cooperative and likely to be monitored regularly

General condition: healthy patient with no general or local pathology;

Oral hygiene: must be satisfactory;

Type of teeth: to reduce the variations, we will limit ourselves to the incisor-canine block.

Non-Inclusion Criteria

We will not include in our study anyone:

Deemed unable to understand the essay, uncooperative or unstable.

With a contraindication to glued ceramic veneers, namely:

Aged teeth;
Abrasive teeth;
Presence of parafunctions;
Unfavorable occlusal relationships;
Poor oral hygiene.

Methods

Type of Study

Our study is a randomized clinical trial comparing three types of crown preparations for bonded ceramic veneers.

During this trial the allocation to the different treatment groups is done at random, by drawing lots, thus ensuring the comparability of these groups.

The same operator will proceed to the draw as follows:

- The distribution in all the different groups will be based on chance;
- We are dealing with two variables the teeth (central, lateral, canine) and the type of preparation (type I, II, III);

Dental Preparation Method for Ceramic Veneers

It differs from conventional preparations in that the retention of the prosthetic element is only ensured by bonding.

*Material Needed for Preparation

The preparation protocols use the concept of controlled tissue penetration through the use of diamond burs calibrated for this purpose.

Several authors have proposed several boxes. Among these authors Bernard Touati, and Galip Gurel.

A set of 3 strawberries is sufficient for a good preparation.
Diamond round bur which delimits the desired indentation in the dentin;
Fillet bur which eliminates grooves and marks the cervical limit;
Red ring cutter: fine grain for finishing.



Figure 1: Cutter Set Selected for the Preparation for Ceramic Veneers (1)

Preparation Methods

Our study is a randomized clinical trial comparing three types of crown preparations for bonded ceramic veneers.

During this trial the allocation to the different treatment groups is done at random, by drawing lots, thus ensuring the comparability of these groups.

The same operator will proceed to the draw as follows:

The allocation to all the different groups will be based on chance;

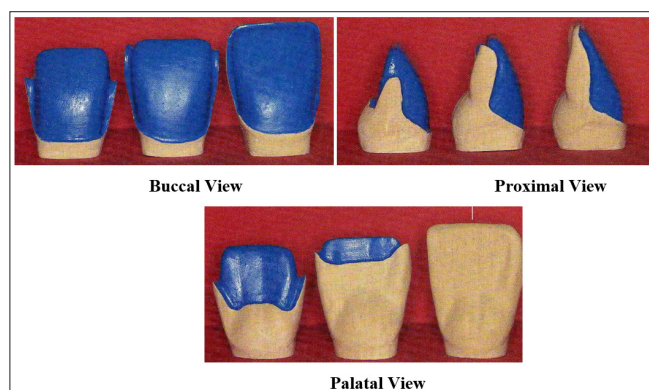


Figure 2: The Three Types of Preparation for Ceramic Veneers on Maxillary Anterior Teeth [1,2].

From left to right preparation in semi-jacket; preparation in slight return; preparation without palatal return.

*Technique for Making Coronary Preparations

To avoid production bias, all of the clinical steps for the ceramic veneers performed in the study (dental preparation, bonding and control) were performed by the same practitioner.

The ceramic veneers were fabricated by a single prosthetist who used the same technique and the same low-melting ceramic (Finesse® All-Ceramic, Ceramco; U.S.A)

All veneers were bonded with Variolink II® (Variolink II, Ivoclar Vivadent, lot no M10683, lot n° M34435, lot n° P22457), a dual curing composite prepared according to the manufacturer's instructions.

Control Sessions

Patients are invited to follow-up sessions after: 6 months, 12 months, 24 months, 36 months, 48 months and 60 months.

During these appointments, the veneers were visually inspected and evaluated according to the criteria studied.

Clinical Case

An 18-year-old female patient consulted for improvement of her smile: Dean's type II dental fluorosis. This well-informed patient requested ceramic veneer treatment.

Before this stage of fluorosis, prosthetic restoration is the rule and ceramic veneers represent the most conservative form.

Clinical examination revealed:

Dean's Class II dental fluorosis

An agenesis of the 13 parallel to a 22 which is small.

An irregularity of the levels of the collars.

A non-gingival smile: full lips



Figure 3: Initial Situation



Buccal View
Proximal View
Figure 4: Coronary Preparation



Figure 5: Final Result After Gluing the Veneers

The 13 transformed into lateral: only a preparation with incisal overlap could make this possible. A better aesthetic result could have been obtained in association with periodontal surgery which would aim to correct the alignment of the necks.

The full lips and the non-gingival smile observed in the patient made it possible to alleviate this problem.

Results

In this study 264 veneers were placed in 73 patients represented by 52 women and 21 men.

The mean age of patients at the start of treatment was 27 years with a range of 13 to 49 years.

The number of veneers varies from “one” to “six” per patient. All veneers were performed at the level of the upper anterior block.

Once the treatment is finished, patients are invited to come back if there is a problem with their veneers or abutment teeth.

Patients will be checked after 6 months; 12 months ; 24 months; 36 months; 48 months; 60 months. The information collected during these checks is reported on the clinical sheet.

All the patients participated in the various controls, only one patient, who benefited from two restorations at the power plants did not participate in the study and this from the second booster (12 months), which is equivalent to a rate abandonment or loss of follow-up in 1.40% of patients (0.76% of restorations).

Descriptive Study

Distribution of the Population by Sex

Table 1: Distribution of Patients by Sex

Sex	Effective	Percentage
Feminine	52	71,23 %
Male	21	28,76 %
Total	73	100,00 %

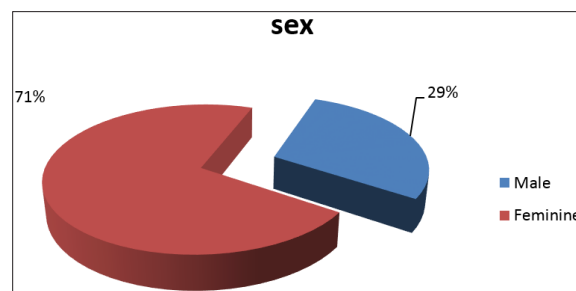


Figure 6: Distribution of Patients by Sex

The sample studied shows a predominance of the female sex with a number of 52 women among 73 patients, which represents 71.23% of the total number. The male sex, numbering 21 men, has a frequency of 28.76%.

Distribution of the Population by Age

Our population includes patients aged 13 to 49 years. The age groups are broken down as follows:

Table 2: Distribution of Patients by Age

Age group (year)	Effective
[12, 14[01
[14, 16[02
[16, 18[01
[18, 20[05
[20, 22[06
[22, 24[09
[24, 26[07
[26, 28[09
[28, 30[08
[30, 32[05
[32, 34[03
[34, 36[07
[36, 38[02
[38, 40[02
[40, 42[01
[42, 44[01
[44, 46[02
[46, 48[01
[48, 50[01

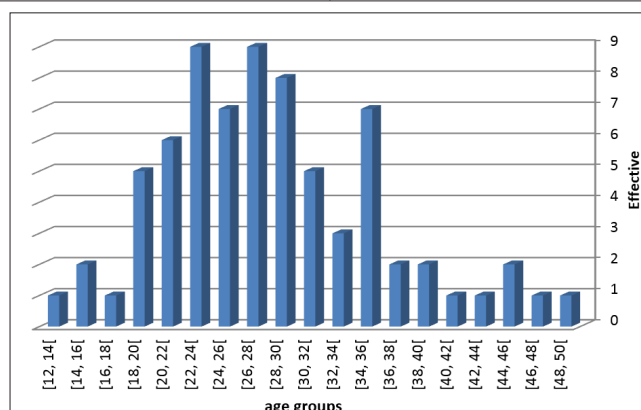


Figure 7: Distribution of Patients by Age

The average age of our study population is 27.71 years; (95% CI = [25.90 years; 29.52 years]). The median age of the sample is 27 years with a minimum age of 13 and maximum age of 49.

➤ Number of Veneers Depending on the Type of Prepared Tooth

Table 3: Number of Veneers by Type of Prepared Tooth

Type of tooth	Numbers	Percentage
Central incisor	120	45,45 %
lateral incisor	86	32,58 %
Canine	58	21,97 %
Total	264	100,00 %

120 central incisors (11 and 21) were treated with ceramic veneers, which represent 45.45% of all facets. 32.58% represents the percentage of lateral treated veneers while the canines represent only 21.97% of the whole.

➤ Distribution of Veneers According to the Character of the Non-Filled Tooth / Filled Tooth

Table 4: Frequency of Veneers According to the Character of the Tooth Not Filled / Filled Tooth

Dent pilier	Effective	Pourcentage
non-obtured	208	78,79 %
obtured	56	21,21 %
Total	264	100,00 %

The veneers were bonded to 208 non-filled teeth, corresponding to 78.79% of all teeth, while 56 of the veneers were bonded to filled teeth, or 21.21%.

Distribution of the Occurrence of Cracks, Fractures, Detachments, Pulpitis, Abutment Tooth Fractures According to the Non-Obtured / Obtured Nature

Table 5: Frequency of the Occurrence of Cracks, Fractures, Detachments, Pulpitis, Abutment Tooth Fractures According to the Non-Obtured / Obtured Nature

Characteristics of the tooth	Crack, fracture, detachment, pulpitis, abutment tooth fracture		Total
	No	yes	
Not obtured	199	9	208
	95,67%	4,33%	100,00%
Obtured	46	10	56
	82,14%	17,86%	100,00%
Total	245	19	264
	92,80%	7,20%	100,00%

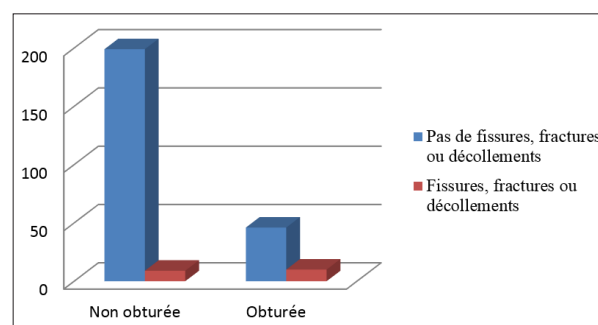


Figure 8: Histogram of the Occurrence of Cracks, Fractures, Detachments According to the Character of the Filled Tooth / Non-Filled Tooth

The occurrence of cracks, fractures, facet detachments was observed with a percentage of 4.33% on the non-filled teeth and in 17.86% of the filled teeth.

Distribution of the Type of Preparation According to the Composite Fillings

Table 6: Frequency of Preparation Type According to Composite Fillings

Type de préparation dentaire	composite filling	Effective	Percentage
Type I	Absence	72	82,80%
	Présence	15	17,20%
	Total	87	100,00%
Type II	Absence	73	79,30%
	Présence	19	20,70%
	Total	92	100,00%
Type III	Absence	66	77,60%
	Présence	19	22,40%
	Total	85	100,00%

Composite filling is an important consideration when dealing with ceramic veneer restorations.

The three types of preparation were carried out mainly on teeth which did not present composite fillings: type I at 82.80%; type II at 79.30% and type III at 77.60%.

Distribution of the Occurrence of Cracks, Fractures, Detachments, Pulpitis, Abutment Tooth Fractures According to the Non-Obtured / Obtured Nature.

Table 7: Frequency of the Occurrence of Cracks, Fractures, Detachments, Pulpitis, Abutment Tooth Fractures According to the Non-Obtured / Obtured Character

Caractéristiques de la dent	Crack, fracture, detachment,		Total
	Non	Oui	
Not obtured	199	9	208
	95,67%	4,33%	100,00%
obtured	46	10	56
	82,14%	17,86%	100,00%
Total	245	19	264
	92,80%	7,20%	100,00%

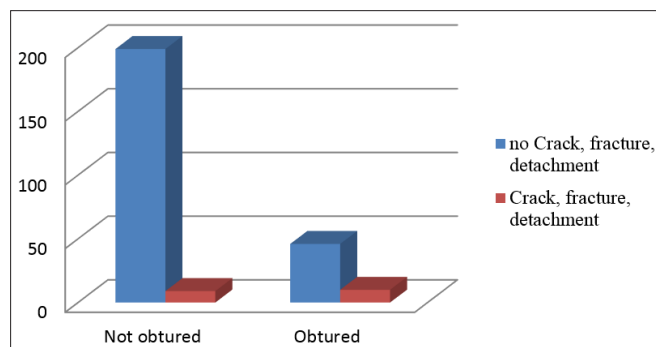


Figure 9: Histogram of the Occurrence of Cracks, Fractures, Detachments According to the Character of the Filled Tooth / Non-Filled Tooth

The occurrence of cracks, fractures, facet detachments was observed with a percentage of 4.33% on the non-filled teeth and in 17.86% of the filled teeth.

Analytical Study

Although Kaplan-Meier statistics were originally designed to deal with individuals, the use of the tooth as a statistical unit instead of the person is justified [3].

In the present study, the Kaplan-Meier analysis was done in two different ways: the first analysis is related to the patient, the second was performed using the restoration as the statistical unit.

Our study is a clinical trial where we seek to evaluate the effectiveness of one type of preparation compared to two other types and this by comparing the results obtained in each group.

Faced with a difference observed between the groups, there are two possibilities either this difference is due solely to chance, or this observed difference is real.

We applied the “Chi2” test to check the dependence or not between the variables and the different groups. This probability is called “p”. The p-value is the threshold from which the observed difference is considered to be statistically significant. This means that it is real and has a low chance of being due to chance. When $p \leq 0.05$ the difference is significant. When $p > 0.05$ the difference is not significant.

Veneer Survival Rate According to the Character of the Tooth not Filled / Tooth Filled

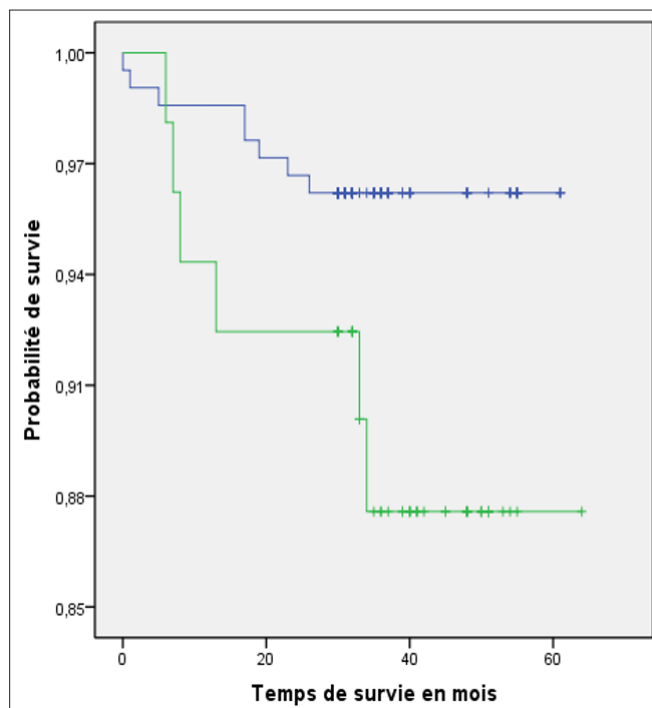


Figure 10: Survival Curve of Ceramic Veneers According to Character (closed / unblocked)

The survival rate of unblocked teeth is 96.20% (95% CI; [93.70%; 98.80%]) with an average survival time of 59.20 months (95% CI; [57.95 months; 60.45 months]).

The survival rate on filled teeth is 87.60% (95% CI; [78.70%; 97.50%]) with an average survival time of 58.33 months (95% CI; [54.00 months; 62.66 months]).

The overall survival rate of ceramic veneers according to the “unblocked / closed” criterion is 90% with an average survival time of 53.33 months (95% CI; [54.00 months; 62.66 months]).

The Log-rank test for the occurrence of events according to the healthy / mortified character gives a $p = 0.05$ and therefore the difference is significant.

Therefore, the presence of composite fillings may have an impact on the survival rate of the veneers in our study.

Discussion

Our study; is a randomized clinical trial comparing three types of crown preparations for bonded ceramic veneers.

We are interested in the role that the design of the coronary preparation can play on the longevity of ceramic veneers.

These restorations, whose translucency meets current aesthetic requirements, are increasingly in demand, but little information, little clinical work is available on this subject.

Our population size includes 73 patients. Analysis of our sample shows a predominance of the female sex with a number of 52 women representing 71.23% of the total workforce and 21 men representing 28.76%.

This predominance of the female sex is explained by the fact that women are more concerned about their appearance than men. They are aware of the role that a beautiful smile can play. Well informed, they demand not only aesthetics but also the least mutilating possible size of their teeth.

Our results are in agreement with the study carried out by Dumfabrt Herbert where the majority of patients were female (60%). It also confirms that these results have been reported in other clinical evaluations on ceramic veneers.

The average age of our study population is 27.71 years. The median age of the sample is 27 years with a minimum age of 13 and maximum age of 49.

This is a young population: at this age group, patients are very concerned about their appearance, which the study by Hamzawi-Decharrière et al. (2007) where they announced that aesthetic demand over the next five years will represent 60% of the reasons for consultation, especially among young patients.

Impact of Composite Fillings on the Survival of Ceramic Veneers

In our study, 264 teeth were restored with ceramic veneers: 208 non-filled and 56 filled teeth:

The survival rate of unblocked teeth is 96.20% (95% CI; [93.70%; 98.80%]) with an average survival time of 59.20 months (95% CI; [57.95 months; 60.45 months])

The survival rate on filled teeth is 87.60% (95% CI; [78.70%; 97.50%]). with an average survival time of 58.33 months (95% CI; [54.00 months; 62.66 months]);

The overall survival rate for ceramic veneers according to the "unblocked / filled" criterion is 90% with an average survival time of 53.33 months (95% CI; [54.00 months; 62.66 months]).

The Chi-square test of the occurrence of events according to the unobstructed / obturated character gives a $p = 0.05$ ($p \leq 0.05$) so the difference is significant: the presence of composite fillings has an impact on the rate of facet survival in our study.

In the documentation consulted; Although investigators evaluated the effect of the design of the ceramic veneer preparation, little information is available regarding the design of the preparation in association with the condition of the existing tooth structure.

Among the risk factors for a higher number of premature loss of

ceramic veneers, as mentioned in the literature, the presence of fillings on the teeth concerned (Dunne & Millar 1993; Shaini et al. 1997), a significant loss of hard dental tissue existing before the start of veneer treatment (Dunne & Millar 1993) [4].

In the articles consulted we find that:

Calamita M. A in a retrospective study concluded that among the 42 failures, only 3 occurred at the level of the teeth with restorations, and no significant association could be observed between the failure and the presence of a restoration [5].

Dumfahrt and Schaffer (2000) by analyzing 205 ceramic veneers in 72 patients concluded that the failure rate increased ($p < 0.01$) when the finish line crossed an existing filling and ($p = 0.058$) when parts of the preparation surface were in the dentin. The weak link in the veneer bond was considered the dentin / glue bond [3].

Guessa P. C, Stappert C. F.J (2008) state that the presence of composite fillings cannot increase the loss of veneers in their study, they even had a negative impact on the overall clinical performance. At the underlying vulnerable ceramic / tooth / composite interfaces, strong marginal discoloration was noted in 12 restorations [3,6,7].

They explain this by the presence of gaps in the physico-mechanical properties of the composite resin, such as polymerization shrinkage, elasticity, high coefficient of thermal expansion and limited wear resistance. On the other hand, the bond of the ceramic to the composite restoration is inferior compared to the bond to enamel or dentin. Finally, the high thermal expansion (inter-proximal) of composites has a negative influence on marginal adaptation. During large temperature changes, the contraction and expansion of composites results in tensile and compressive stresses at the edge of the ceramic veneers with loss of bond, deformation of the veneer margins and the formation of cracks as a result. Thermal stresses can be minimized by partially or fully encompassing pre-existing composite restorations.

Karlsson (1992) reports that the presence of composite seems to increase the risk of infiltration. In addition the connection of the composite to the dentin; at the restoration-dentin interface, may be the weakest link

Murphy et al. (2005) in a 5-year retrospective evaluation that included 29 patients, 62 veneers reported a correlation between failure and the presence of pre-existing composite restorations [3].

Peumans et al. (2004) in their clinical study on the evaluation of the clinical performance of ceramic veneers after 5 and 10 years of clinical service and knowing that fillings were present in 70% of the ceramic veneers in their study; reported that the presence of composite does not appear to influence veneer retention even after 10 years. They explained this in part by the in vitro results of Magne et al. which showed that respect for the original tooth in fractured teeth was almost restored when the composite was used to replace the missing dentin, with the ceramic acting only as a substitute for the enamel [7,8,9].

Shaini F.J; Shortanll A.C.C; Marquis P.M observed increased failure rates and the development of problems when ceramic veneers were bonded to existing composite restorations [10].

In addition, a numerical study has shown that the partial or total envelopment of composite fillings is indicated to minimize thermal stresses. With medium or long type ceramic proximal

wraps, part of the composite volume is replaced by ceramic, which decreases the influence of expansion or contraction of the underlying composite filling [11].

A study done in 1991. This study investigated a load applied to a bonded veneer to the tooth, where the underlying incisal edge is either a bonded fragment, a composite restoration, or the intact tooth. The force at which the break occurs in the facet; as seen in the tooth as well, depends on its flexural strength, the modulus of elasticity of the underlying material, the dimensions and the strength of the bonds between the materials. She reported in contrast, a significantly higher tensile strength in the absence of initial treatment and the fractured incisal edge was restored with a layered veneer. The fracture resistance of the veneered restoration directly on the fractured tooth was not different from that of intact teeth restored with veneers [12].

Then in study Magne and Douglas evaluate the distribution of the stresses for teeth presenting coronary fractures. These teeth were divided into two groups: teeth restored with ceramic veneers after composite reconstruction, and teeth restored with ceramic veneers only. The results show that the prior restoration of decayed teeth is a technique ensuring better flexibility. Another study shows that the resistance to fracture of ceramic is influenced by the modulus of elasticity of the material used for the reconstruction [13,14].

Our results are in agreement with those of Dunne & Millar 1993, Dumfahrt and Schaffer (2000); Murphy et al. (2005) ; Shaini et al. 1997 [15,16,17].

In our study, the influence of composite restorations on the longevity of ceramic veneers can be explained by the physico-mechanical properties of the composite resin which have shortcomings, such as polymerization shrinkage, elasticity, coefficient of thermal expansion high and limited wear resistance. When ceramic is applied to enamel, the more rigid substrate absorbs the stress due to the function and prevents the ceramic from fracturing. Conversely, when ceramic is applied to the composite resin, the stress will be absorbed by ceramic which will fracture due to its fragile nature.

On the other hand, the bond of the ceramic to the composite restoration is weaker compared to the bond to enamel or dentin. The high thermal expansion of composites has a negative influence on the marginal fit. During large temperature changes, the contraction and expansion of composites results in tensile and compressive stresses on the margins of the ceramic veneers with loss of bond, deformation of the facet margins and the formation of cracks as a result. Thermal stresses can be minimized by partially or fully encompassing pre-existing composite restorations.

Conclusion

Within the methodological limits of our clinical trial which evaluated 264 veneers placed in 73 patients (52 women and 21 men) of an age range ranging from 13 years to 49 years with an average age of 27.71 years and after 64 months of follow-up (5 years and 4 months), the presence of composite restorations is a risk factor for the production of ceramic veneers.

References

1. Faucher AJ, Kouby gF (2001) Pignolych, Dyschromies dentaires : de l'éclaircissement aux facettes en céramique, Editeur quintessence internationale.
2. Gurel G (2005) Les facettes en céramique : de la théorie à la pratique ; traduit par Francine Liger et Simon Permulter, Editeur Quintessence Internationale .

3. Mangani F, Cerutti A, Putignano A, Bolero R, Madini L (2010) Clinical approach to anterior adhesive restorations using resin composite veneers, The European Journal of Esthetic Dentistry 2: 120- 137.
4. Ortet Stephanie, Jean Christophe Paris, Andre Jean Fauchier (2008) Les transitoires à partir des masques : un préalable incontournable en facette céramique collée, Revue fil dentaire, novembre 37: 44-46.
5. Robbins JW (1991) Maquillage des facettes céramiques, Clinic Odontologia 6: 435-438.
6. Magne P, Douglas WH (1999) Design optimization and evolution of bonded ceramics for the anterior dentition: a finite-element analysis, Quintessence Int 30: 661-672.
7. Modica D, Pellerine (1994) Facettes IPS Empress: la solution, Revue information dentaire 76: 1497-1503.
8. Magne Pascal (1999) Optimisation des concepts mécaniques en médecine dentaire esthétique, Information dentaire; 10 février 6: 373-381.
9. Magne P, Douglas WH (1999) Design optimization and evolution of bonded Ceramics for the anterior dentition: a finite-element analysis. Quintessence Int 30: 661-672.
10. Magne P, Magne M (1999) Facettes en céramique à l'aube de l'an (2000) : une fenêtre ouverte sur la biomimétique ,Revue réalité Clinique 1: 329-342.
11. Hui KK, Williams B, Holt RD (1991) A comparative assessment of the strengths of porcelain veneers for incisor teeth dependent on their design characteristics, Br Dent J 1: 51-55.
12. Konrad H (2010) Meyenberg, No vital teeth and porcelain laminate veneers -a contradiction?, The European Journal of Esthetic Dentistry 2: 154-168.
13. Fradeani M (2007) Réhabilitation esthétique en prothèse fixée I: une analyse esthétique ,Editeur Quintessence Internationale.
14. Miara Alexander, Miara Paul (2006) Traitement des dyschromies en odontologie. Editeur cdp.
15. Dunne S, Millar B (1993) A longitudinal study of the clinical performance of porcelain veneers, Br Dent J 1: 317-321.
16. Dumfahrt H, Schäffer MH (2000) Porcelain laminate veneers, a retrospective evaluation after 1 to 10 years of service: part II, Clinical results ,The International Journal of Prosthodontics 13: 9-18.
17. Murphy E, Ziada HM, Allen PF (2005) Retrospective study on the performance of porcelain laminate veneers delivered by undergraduate dental students, Eur J Prosthodont Restor Dent 13: 38-43.
18. Shaini FJ, Shotall ACC, Arquis PMM (1997) Clinical performance of porcelain laminate veneers: a retrospective evaluation over a period of 6, 5 years, Journal of oral rehabilitation 24: 553-559.

Copyright: ©2022 Soraya Dendouga. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.